

# Technical data sheet

011121MBA

Cored welding wire

# CHROMECORE 414N-S



## CLASSIFICATION

EN 14700: T Fe7

## DESCRIPTION

- Tubular wire for submerged arc hardfacing
- Nitrogen-containing martensitic stainless steel weld deposit optimised for corrosion resistance
- The deposit resists corrosion, wear, galling and thermal fatigue

## APPLICATIONS

- Hardfacing parts undergoing corrosion, erosion, abrasive wear and thermal shocks

### Examples:

Continuous casting rolls, valve seats, valve gates, valve wedges, safety valves

## TYPICAL ALL-WELD METAL ANALYSIS


C	Mn	Si	Cr	Ni	Mo	N
0.05	1.2	0.9	13.5	3.4	1.0	0.1

Structure: martensite

## HARDNESS (3-LAYER DEPOSIT)

As welded: 40 - 45 HRc

## TEMPER CURVES

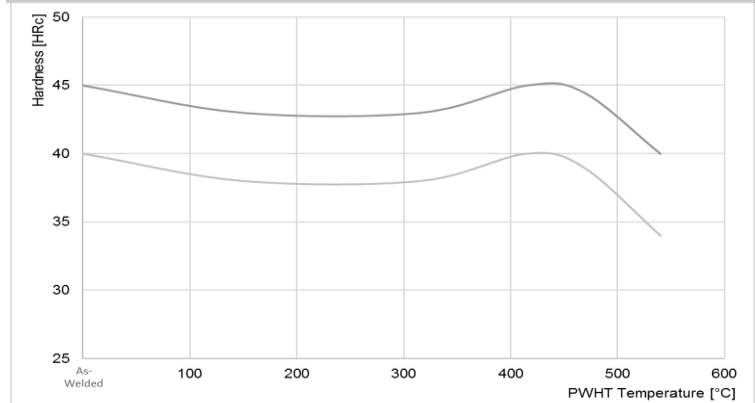

## FLUX DESCRIPTION

	WA FLUX 325	WA FLUX 385	WA FLUX 415	WA ULTRAFLUX
EN ISO 14174 class	S A AB 1 65	S A AF 2 64	S A FB 1 55	S A FB 1 55

## OPERATING CONDITIONS

Diameter (mm)	Current (A)		Voltage (V)		Stick-out (mm)	
	Range	Optimum	Range	Optimum	Range	Optimum
2.4	200 - 450	350	26 - 30	30	25 - 60	30
2.8	250 - 550	400	28 - 32	30	25 - 60	30
3.2	300 - 650	500	28 - 32	30	25 - 60	30

Recovery: 95%

Current type/polarity: DC+ or DC-

## WELDING POSITIONS

Flat

## PACKAGING

Diameter	≥ 2.4 mm	
Standard packaging	B 450 coil	Drum
Weight	25 kg	Up to 330 kg

Other packaging and other diameters: please consult us